

Northumbria Research Link

Citation: Alkhalifah, Mohammed A., Howchen, Benjamin, Staddon, Joseph, Celorrio, Veronica, Tiwai, Devendra and Fermin, David J. (2022) Correlating Orbital Composition and Activity of $\text{LaMn}_x\text{Ni}_{1-x}\text{O}_3$ Nanostructures Towards Oxygen Electrocatalysis. *Journal of the American Chemical Society*, 144 (10). pp. 4439-4447. ISSN 0002-7863

Published by: American Chemical Society

URL: <https://doi.org/10.1021/jacs.1c11757> <<https://doi.org/10.1021/jacs.1c11757>>

This version was downloaded from Northumbria Research Link:
<https://nrl.northumbria.ac.uk/id/eprint/48590/>

Northumbria University has developed Northumbria Research Link (NRL) to enable users to access the University's research output. Copyright © and moral rights for items on NRL are retained by the individual author(s) and/or other copyright owners. Single copies of full items can be reproduced, displayed or performed, and given to third parties in any format or medium for personal research or study, educational, or not-for-profit purposes without prior permission or charge, provided the authors, title and full bibliographic details are given, as well as a hyperlink and/or URL to the original metadata page. The content must not be changed in any way. Full items must not be sold commercially in any format or medium without formal permission of the copyright holder. The full policy is available online: <http://nrl.northumbria.ac.uk/policies.html>

This document may differ from the final, published version of the research and has been made available online in accordance with publisher policies. To read and/or cite from the published version of the research, please visit the publisher's website (a subscription may be required.)



**Northumbria
University**
NEWCASTLE



UniversityLibrary

Correlating Orbital Composition and Activity of $\text{LaMn}_x\text{Ni}_{1-x}\text{O}_3$ Nanostructures Towards Oxygen Electrocatalysis

Mohammed A. Alkhalifah,¹ Benjamin Howchen,¹ Joseph Staddon,^{1,2} Veronica Celorrio,³
Devendra Tiwari^{1,4*} & David J. Fermin^{1*}

¹ School of Chemistry, University of Bristol, Cantocks Close, Bristol BS8 1TS, UK

² Current affiliation: Johnson Matthey, 10 Eastbourne Terrace, London, W2 6LG, UK

³ Diamond Light Source Ltd., Diamond House, Harwell Campus, Didcot OX11 0DE, UK

⁴ Department of Mathematics, Physics & Electrical Engineering, Northumbria University, Newcastle upon Tyne NE1 8ST, UK

ABSTRACT


The atomistic rationalization of the activity of transition metal oxides towards oxygen electrocatalysis is one of the most complex challenges in the field of electrochemical energy conversion. Transition metal oxides exhibit a wide range of structural and electronic properties, which are acutely dependent on composition and crystal structure. So far, identifying one or several properties of transition metal oxides as descriptors for oxygen electrocatalysis remains elusive. In this work, we performed a detailed experimental and computational study of $\text{LaMn}_x\text{Ni}_{1-x}\text{O}_3$ perovskites nanostructures, establishing an unprecedented correlation between electrocatalytic activity and orbital composition. The composition and structure of the single-phase rhombohedral oxide nanostructures are characterized by a variety of techniques, including X-ray diffraction, X-ray absorption spectroscopy, X-ray photoelectron spectroscopy and electron microscopy. Systematic electrochemical analysis of pseudocapacitive responses in the potential region relevant to oxygen electrocatalysis shows the evolution of Mn and Ni *d*-orbitals as a function of the perovskite composition. We rationalize these observations on the basis of electronic structure calculations employing DFT with HSE06 hybrid functional. Our analysis clearly shows a linear correlation between the OER kinetics and the integrated density of states (DOS) associated with Ni and Mn *3d* states in the energy range relevant to operational conditions. On the other hand, the ORR kinetics exhibits a second-order reaction with respect to the electron density in Mn and Ni *3d* states. For the first time, our study identifies the relevant DOS dominating both reactions and the importance of understanding orbital occupancy under operational conditions.

Corresponding Authors

Devendra Tiwari – devendra.tiwari@northumbria.ac.uk

David J. Fermin – david.fermin@bristol.ac.uk

TOC

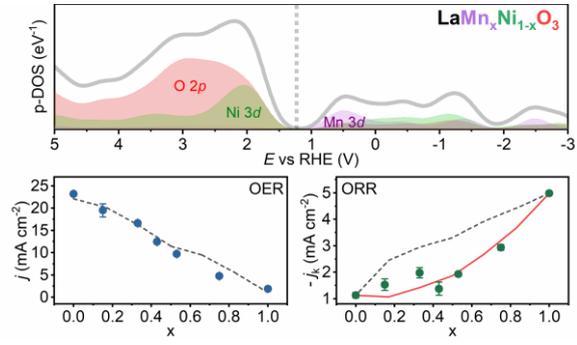

Introduction

The electrochemical oxygen reduction (ORR) and oxygen evolution reactions (OER) are complex multi-electron and proton transfer reactions that underpin key energy conversion and storage devices such as fuel cells, electrolyzers, and metal-air batteries.¹⁻⁴ One of the main challenges in this area is the design of electrocatalysts composed of Earth-abundant elements capable of driving these reactions at a high rate and low energy input (voltage).⁵⁻⁸ Toward this goal, transition metal oxides offer a wide range of structural motifs and electronic properties which are acutely dependent on composition. However, correlating these structural and electronic properties, amenable to a wide range of microscopy and spectroscopy tools as well as first-principles electronic structure calculations, to their electrocatalytic performance remains a formidable challenge.

Significant efforts have been devoted to correlating the electronic properties of oxides to the oxygen binding energy as a proxy for electrocatalytic activity. This approach has been used to rationalize the performance of perovskites oxides (general formula ABO_3) to (i) e_g orbital occupancy,^{9, 10} (ii) B-O orbital hybridization (covalency),^{11, 12} (iii) energy of formation of oxygen vacancies.¹³⁻¹⁶ One of the appealing aspects of this strategy is the possibility of linking properties such as the metal d -band and O p -band centres to electrocatalytic activity (via oxygen binding energy),^{17, 18} which could pave the way for high-throughput computational material screening. However, this strategy fails to recognize the complexities associated with electrochemical interfaces and the fact that the electronic structure/property of the material can be significantly altered by the electrode potential (Fermi level) under operational conditions.¹⁹⁻²¹ This aspect has been elegantly illustrated by the recent report on correlative operand microscopy of $Co(OH)_2$ platelets.²² At a fundamental level, electron transfer kinetics are determined by the overlap in the energy scale of the density of states of redox molecules in solution and the solid-state material, as elegantly described by the Gerischer model for interfacial electron transfer.²³ Therefore, a more fundamental approach to probing the electrocatalytic activity of transition metal oxides is to establish the link between the observed electrocatalytic activity and the element-projected density of states (p-DOS) of these strongly correlated materials across the energy (potential) range relevant to oxygen electrocatalysis. This approach has been used to rationalize the electrocatalytic activity of perovskites and pyrochlores, identifying Mn-based oxides as a key active element in ORR electrocatalysis.^{24, 25}

$LaMn_xNi_{1-x}O_3$ (LMNO) provides an interesting test case to probe correlations between electronic structure and activity, given the contrasting electrocatalytic properties of Mn and Ni states towards ORR and OER. Bradley and co-workers performed a detailed high-throughput combinatorial analysis of the La-Mn-Ni composition space, concluding that Ni rich-compositions provide optimum oxygen electrocatalysis, although without a clear correlation with the structure or electronic properties.²⁶ Another study investigated the effect of particle size on the electrocatalytic activity of LMNO with Mn content $x = 0.5$.²⁷ In this study, we interrogate, for the first time, the evolution of the electronic structure of the pure rhombohedral LMNO phase as a function of the B-site composition and its correlation with the electrocatalytic activity towards the ORR and OER. We implemented an ionic-liquid based synthesis method that generated particles with crystal domain sizes ranging from 17 to 26 nm,

featuring high phase purity, well-defined composition and comparable geometric surface areas. A combination of quantitative X-ray diffraction (XRD), X-ray absorption spectroscopy (XAS), X-ray photoelectron spectroscopy (XPS) and electron microscopy reveals a monotonic increase of the lattice constant with increasing x (Mn content) as well as subtle changes in the effective oxidation states of the B-sites metals. The composition dependence of the electrocatalytic activity towards OER and ORR were investigated in alkaline solutions, which was rationalized in terms of the density of states associated with Mn and Ni d -orbitals and O- p orbitals. A key element of our approach is the correlation between pseudocapacitive responses in the potential range relevant to oxygen electrocatalysis and the electronic structure of the material calculated by DFT employing HSE06 functional. The combination of experimental and computational analysis not only shows that the activity of these strongly correlated electron systems can be primarily described in terms of the density and energy position of the Mn and Ni d -states but also that ORR shows a higher-order dependence on the electron density at the active sites.

Results

Structure and composition of LMNO nanoparticles. $\text{LaMn}_x\text{Ni}_{1-x}\text{O}_3$ nanoparticles with x ranging from 0 (LaNiO_3) to 1 (LaMnO_3) were prepared by calcination at 700 °C of a precursor containing nitrate salts of the metal cations, EDTA and 1-ethyl-3-methylimidazolium acetate. Detailed synthesis protocols, catalyst formulation and characterization techniques are described in the Method section of the **Supporting Information**. **Figure 1a** shows the XRD patterns across the composition range, characterized by a pure rhombohedral phase ($R\text{-}3\text{C}$ space group). Structure refinement shows a systematic increase of the a and c lattice constants with increasing x values up to approximately 0.5, as summarised in **Table S1** (supporting information). Higher Mn content shows very little change in the lattice constant in agreement with data reported in the structural database.²⁸⁻³⁰ These subtle monotonic changes in the lattice constant are consistent with the fact that Mn and Ni are relatively close to each other in the first row of transition metals, which is an essential consideration throughout our analysis.

The composition of the LMNO particles was examined by inductively coupled plasma – optical emission spectrometry (ICP-OES) and transmission electron microscopy-energy dispersive analysis of X-rays (TEM-EDX), shown in **Table S2** and **Figure S1**, respectively. There is a close correlation between the Ni/Mn ratio in the molecular precursor and the nanostructures after calcination, while a slight La excess is also observed. The TEM-EDX images show that the elemental distribution is highly homogeneous across a cluster of nanoparticles aggregates. Representative TEM images in **Figure S2a** display particle sizes in the range of 17 to 35 nm and clearly defined lattices fringes associated with the $\{110\}$ and $\{102\}$ planes (**Figure S2b**). The particle size range is also consistent with the broadening of the XRD peaks in **Figure 1a**, yielding average crystalline sizes between 17 ± 3 to 26 ± 4 nm. All these features are consistent with the high phase purity of the nanostructures across the composition range.

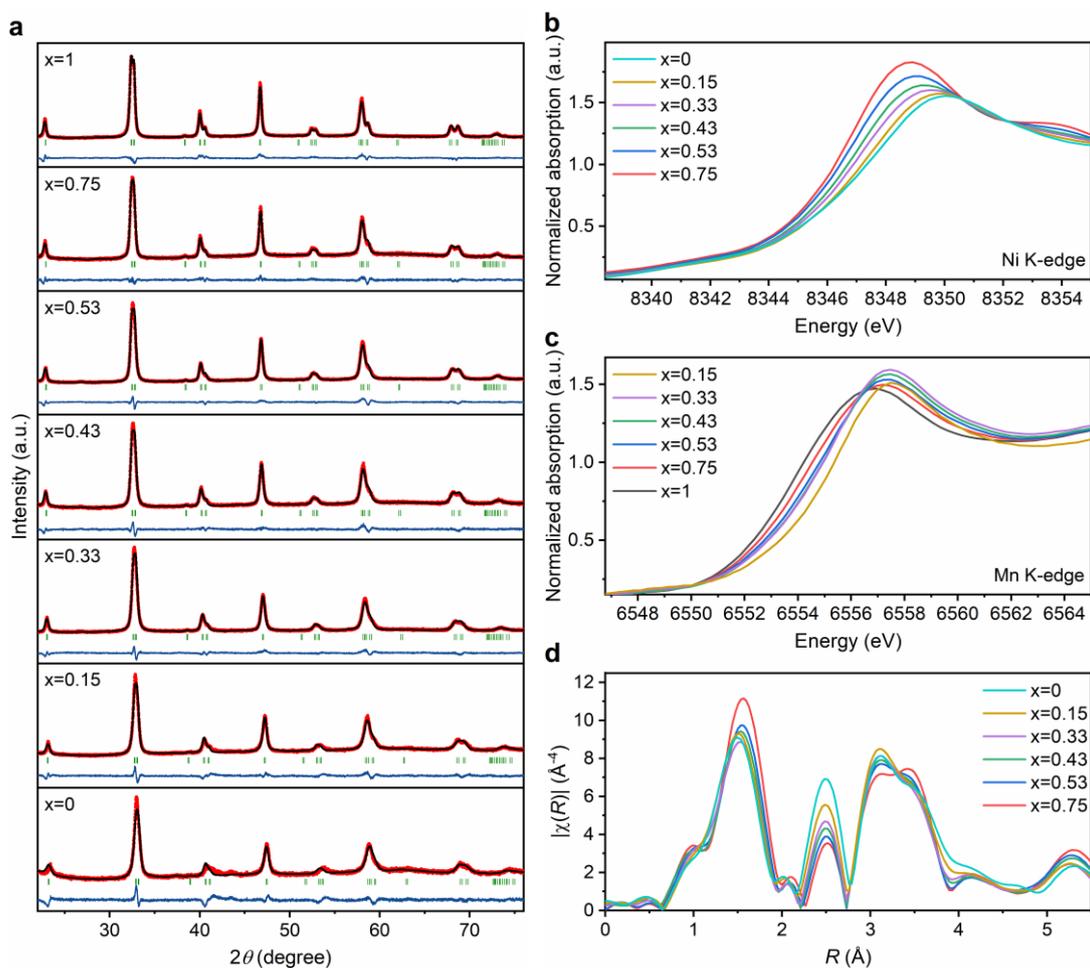


Figure 1 Structure characterization of LMNO Nanostructures. (a) XRD patterns of $\text{LaMn}_x\text{Ni}_{1-x}\text{O}_3$ and Rietveld structure refinement to rhombohedral phase ($R\text{-}3\text{C}$ space group). Structural parameters obtained from the refinement are summarised in **Table S1**. (b) Normalized XANES spectra of Ni K-edge as a function of Mn content in the B-site, showing a decrease in the effective oxidation state of Ni with increasing x value (higher Mn-content). (c) Normalized XANES spectra of Mn K-edge, revealing a relative increase in the effective Mn oxidation state with increasing Mn content; (d) FT (not phase corrected) of the k^3 -weighted EXAFS spectra at the Ni K-edge, showing a slight increase in the Ni – O bond at high Mn content. $E_0 = 8345$ eV; $2.7 < k < 10.2$; Hanning window.

Figures 1b and **1c** contrast the normalized Ni and Mn K-edges of the X-ray absorption near-edge structure spectra (XANES) of the various LMNO particles, respectively. The data show an increase in the energy of the Mn edge, with a concomitant decrease in the energy of the Ni edge, as the Mn content increases. These interesting trends show a degree of electronic interaction between Mn and Ni sites. We have estimated the effective Ni oxidation state from the first derivative of the XANES edge using two different approaches as discussed in **Figure S3a**, revealing a decrease from between 3.1-2.8 in LNO ($x = 0$) to around 2.7-2.5 for $x = 0.75$ (see **Table S3**). Estimation of the effective Mn oxidation state is significantly more complex, often involving the pre-edge feature,³¹ which in our spectra is convoluted with the La L_1 lines as shown in **Figure S3b**. Although the data show a clear increase in the effective Mn oxidation

state with increasing Mn content by the shift of the main edge to higher energies, our current set of data prevents us from establishing a more quantitative analysis. The Fourier transformed Extended X-Ray Absorption Fine Structure (EXAFS) spectra of the Ni K-edge in **Figure 1d** also shows an interesting observation. The first peak at around 1.5 Å (without phase correction) corresponds to the first coordination shell (Ni – O). Quantitative analysis of the first coordination shell (**Figure S4** and **Table S4**) shows that the Ni – O bond distance increases from 1.93 ± 0.03 Å in the case of LNO ($x = 0$) to 2.00 ± 0.02 for the high Mn content ($x = 0.75$) perovskite. The amplitude of the peak around 2.5 Å, which is linked to the Ni-Ni/Mn scattering, decreases with increasing x values. This is an interesting result that we have not been able to fully rationalise, given that there is little contrast between Ni-Mn and Ni-Ni scattering. The third peak, above 3 Å, is a combination of Ni-La and Ni-Ni/Mn single scattering together with multiple scattering. The Mn Fourier transformed of the k^3 -weighted data (**Figure S5**) shows a similar dependence with composition. However, the strong overlap with the La L_1 transition has prevented us from quantitatively approaching this set of data. These observations reveal electronic effects between the B-site cations that manifest in very subtle structural changes, which will require further studies to quantify fully.

Pseudocapacitance features and electrocatalytic activity of LMNO Nanostructures. The evolution of the pseudocapacitance responses as a function of the LMNO nanoparticle composition is displayed in **Figure 2a**. Nanoparticle electrodes were prepared by drop-casting 10 μL of a nanoparticle ink dispersion containing Vulcan XC-72R (Vulcan) and Nafion[®] perfluorinated resin solution (Nafion). Although Morales et al. have shown that Nafion can reduce the oxidation state of Mn in MnFeNiO_x nanoparticles by examining the Mn- L_3 edge,³² this work along with previous LMO ($x=0$) in-situ studies do not provide clear evidence of such effects.²⁵ The electrode loading for all compositions was $398 \mu\text{g cm}^{-2}$ LMNO nanoparticles, $50 \mu\text{g cm}^{-2}$ Vulcan and $50 \mu\text{g cm}^{-2}$ Nafion. The voltammograms in **Figure 2a** are recorded in ultrapure KOH solutions (0.1 mol dm^{-3}) under Ar saturated solutions and a scan rate of 10 mV s^{-1} . As the Mn content decreases, the voltammetric profiles clearly show the emergence of a pseudocapacitance response at potentials above 1.2 V and below 0.5 V, along with the suppression of two peaks between 0.5 and 0.9 V. The redox transition at potentials above 1.2 V observed under high Ni content are commonly described in terms of the transition between Ni^{2+} and Ni^{3+} states,^{26, 33, 34} while the redox peaks between 0.5 and 0.9 V are commonly associated with Mn^{2+} and Mn^{3+} states.³⁵ Recent in-situ X-ray absorption and X-ray emission spectroscopy studies by Celorrio et al. have recently shown changes in the Mn K-edge absorption and $K\beta$ emission spectra consisting with reversible changes in the Mn redox state in LMO nanoparticles in the range of 0.2 to 0.8 V.²⁵ In this work, we link these pseudocapacitance responses to population and depopulation of the density of states associated with Ni and Mn $3d$ states. Conceptually, these phenomena can be correlated to the physics underpinning scanning tunnelling spectroscopy (STS), where changes in the applied potential bias between the tip and substrate allow mapping the electronic bands of the solid. In this case, changes in the applied potential between the working and reference electrodes act as the tip-substrate bias, and the pseudocapacitance responses correspond to the population/depopulation of the orbitals at the surface of these strongly electron correlated materials.

The voltammetric features shown in **Figure 2a** are stable upon consecutive cycling in a potential range between 0 V and 1.9 V vs RHE, suggesting that the surface composition of the oxides does not irreversibly change within the timescale of these experiments. In our previous study, we established close correlation between the voltammetric responses of LMO nanoparticles synthesised at different temperatures and the surface content of Mn in the perovskite lattice as probed by XPS and Low Energy Ion Scattering (LEIS).³⁶ This is a further experimental evidence of the link between pseudocapacitance responses and surface composition of these perovskites. However, we cannot exclude that subtle reconstruction processes at the first atomic layer may take place upon polarisation at the solid/electrolyte interface.²¹

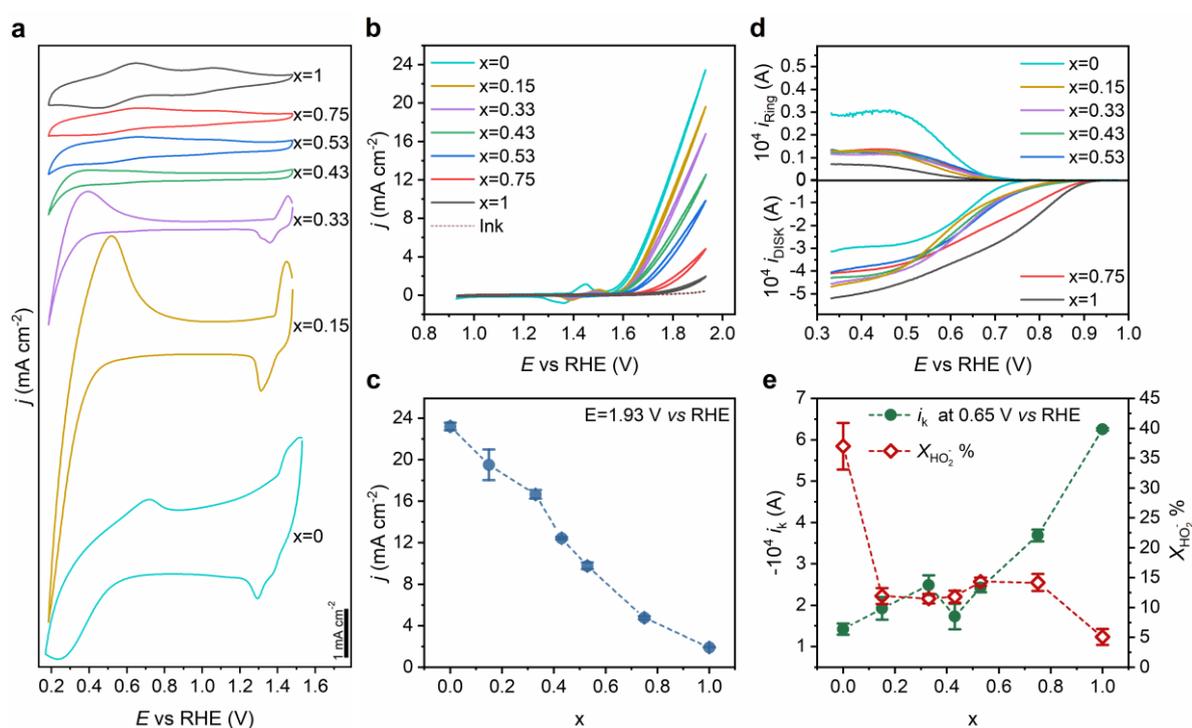


Figure 2 Electrochemical responses and electrocatalytic activity. (a) Pseudocapacitance responses of LMNO catalysts layer at a glassy carbon (GC) electrode in Ar-saturated 0.1 M KOH at scan rate 10 mV s^{-1} . The catalysts layer was deposited as an ink composed of $398 \mu\text{g}_{\text{metal oxide cm}^{-2}}$, $50 \mu\text{g}_{\text{vulcan cm}^{-2}}$ and $50 \mu\text{g}_{\text{Nafion cm}^{-2}}$. (b) Cyclic voltammograms of the electrocatalysts layer in Ar-saturated 0.1 M KOH at scan rate 10 mV s^{-1} between 0.93 and 1.93 V vs RHE. The trace labelled as 'ink' corresponds to the controlled formulation without LMNO nanoparticles. (c) Current density normalized by the geometric electrode surface area at 1.93 V vs RHE as a function of the B-site composition. (d) Rotating ring-disk electrode measurements at 1600 rpm for the various catalysts compositions in O_2 -saturated 0.1 M KOH. The potential GC disk containing the catalysts layer was scanned at 10 mV s^{-1} while the Pt ring was held at 1.10 V. (e) Compositional dependence of the kinetically limited current (i_k) at 0.65 V vs RHE and mean hydrogen peroxide yield (X_{HO_2}) obtained between 0.4 and 0.6 V.

Current-potential curves associated with the OER at a rotating ring-disk electrode (RRDE) are shown in **Figures 2b**. The onset potential for OER shows a monotonic increase with increasing Ni content. The increase in OER activity is also illustrated by the dependence of the current density (normalized by the geometric area) at 1.93 V vs RHE as a function of the composition shown in **Figure 2c**. It should be mentioned that iR compensation has minimal impact on the experimental trends observed. On the other hand, **Figure 2d** shows an increase in the onset potential for the ORR in O_2 saturated solution with increasing Mn content. It is also observed that the diffusion limited current in the case $x = 1$ (LMO) is significantly higher than for $x = 0$ (LNO), while intermediate compositions show similar currents. This trend reflects the ratio of 2 vs 4 e^- ORR pathways as a function of composition. Indeed, this observation is consistent with the values of the ring current (**Figure 2d**), which is proportional to the rate of hydrogen peroxide HO_2^- formation at the disk electrode. **Figure 2e** shows the average HO_2^- yield ($X_{HO_2^-}$) between 0.4 and 0.6 V vs RHE, calculated from the ratio of the ring to disk currents (see Methods). Interestingly, $X_{HO_2^-}$ sharply decreases upon introducing Mn sites into the perovskite lattice, becoming weakly dependent on composition. The kinetically limited current (i_k) obtained from Koutecky-Levich (**Figure S6**) analysis at 0.65 V vs RHE as a function of B-site composition is also illustrated in **Figure 2e**. Although i_k increases with increasing Mn content, the relationship appears non-linear. The contrasting trends between the OER and ORR kinetics with B-site composition strongly suggest different mechanistic pathways for these reactions. We will come back to this important observation in the Discussion section.

Composition dependence of the LMNO electronic structure. In view of the strongly electron correlated nature of these oxides, the electronic structure of LMNO as a function of composition was calculated by DFT employing HSE06 hybrid functional. The supercell illustrated in **Figure 3a** contains 120 atoms (videos illustrating the supercell can be also be found in the **Supporting information**), which allows introducing B-site composition x of 0, 0.17, 0.33, 0.50, 0.66, 0.75, 0.83 and 1. A GGA-PBE functional with a Monkhorst-Pack k -point grid of spacing $< 0.025 \text{ \AA}^{-1}$ and norm-conserving pseudopotentials are implemented with an energy cut-off of 1700 eV, employing a spin-polarized scheme with GGA-PBE functional and Hubbard model for structure optimization (see Methods). The optimized structures in the $R-3C$ space group yield lattice parameters very close to the experimental values as displayed in **Figure 3b**, with differences of less than 1.3%. The calculated values show a smooth monotonic change of the structural parameters, which is to be expected when replacing Ni by Mn in a rhombohedral perovskite crystal. The small differences between experimental and calculated cell parameters can be partly linked to the fact that the former are measured at room temperature, while structure optimisation is done at 0 K. It should also be mentioned that cationic vacancies on these materials can lead to non-monotonic changes in lattice constants as reported by Blasco et al.²⁹

The element-projected density of states (p-DOS) as a function of composition are displayed in **Figure 3c**. We will focus our discussion on the features associated with Mn and Ni $3d$ orbitals as a function of LMNO composition, which can be linked to the pseudocapacitive features observed in **Figure 2a**. The first challenge to address is the reference scales. The calculated E_f is held at the maximum of filled states, while in electrochemical experiments is a complex dependence of surface orientations, reconstruction, composition (which determines the effective work functions) and, crucially, the electrode potential. The region in which the DOS is most sensitive to the composition of the material is between -3.0 and 1 eV vs the calculated E_f . Most of the features observed in the p-DOS in this region

mirror the pseudocapacitive responses observed in **Figure 2a**. For instance, as x increases, we can see the emergence of the Mn $3d$ states at energies above -2 V, while at low x values (Ni-rich) there is the emergence of Ni $3d$ states. These are key observations that allow us to postulate that, under operational conditions, the electrode potential controls the occupancy of the DOS in this energy region.

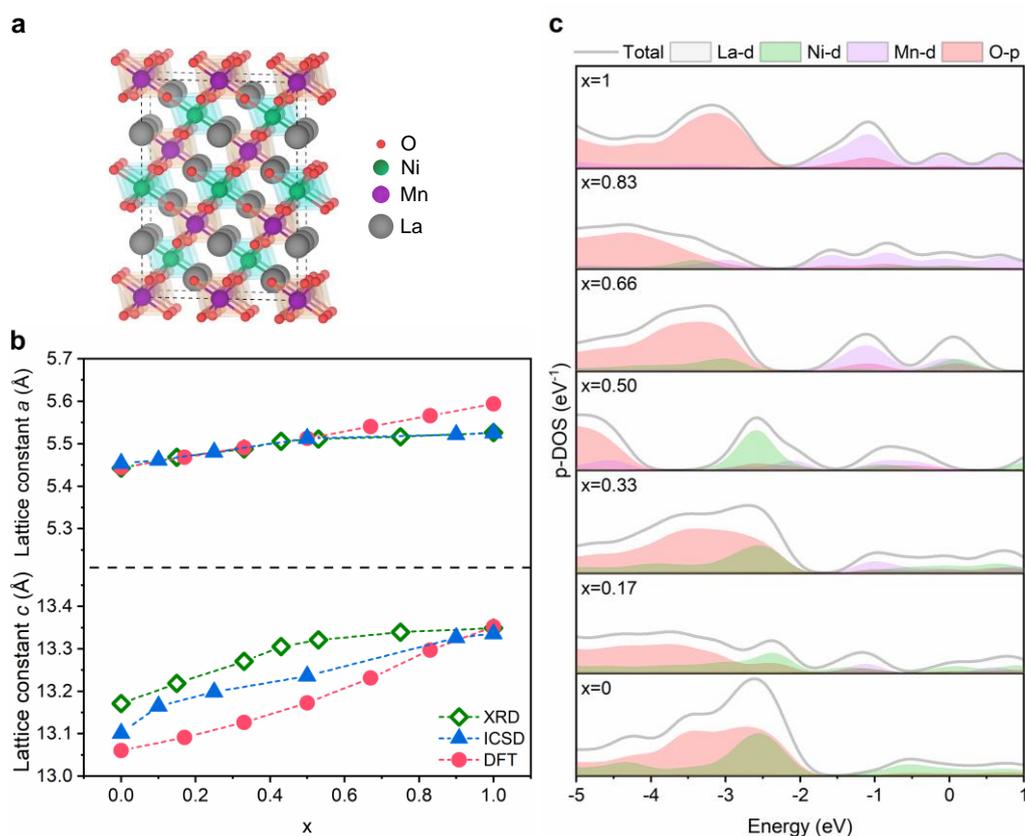


Figure 3 Electronic structure calculations. (a) Optimized 120 atom supercell used in electronic structure calculation for LMNO, featuring La (grey), Ni (green) and Mn (purple), and O (red). (b) Crystal lattice constant a and c as a function of Mn content x obtained from XRD refinement (this work), DFT+U structure optimization (this work) and from the Inorganic Crystal Structure Database (ICSD) files with the following collection numbers (measurement temperature): 67714 (1.5 K), 154963 (293 K), 154964 (293 K), 154969 (293 K), 154975 (293 K), 55953 (293 K). (c) Element-projected DOS (p-DOS) calculated using hybrid DFT with HSE06 functional.

Discussion

The electrochemical responses in **Figure 2** provide clear evidence that changes in the applied potential (i.e. shifting the Fermi level) leads to populating and depopulating electronic states in the oxides as recently discussed by Costentin et al.³⁷ Indeed, the electrochemical (pseudocapacitance) responses associated with Ni $3d$ and Mn $3d$ states allow rescaling the p-DOS energy range with respect to the RHE as shown in **Figure 4a**. The dotted line at 1.23 V vs RHE allows demarcating two regions in which orbital occupancy determines the ORR and on the OER kinetics. As the potential is increased above

the demarcation line (E_f is decreased), orbitals are depopulated, triggering the OER. The depopulated states can be considered as *holes* in the context of semiconductor materials. On the other hand, sweeping the potential to negative values with respect to demarcation line will lead populating states with electrons promoting the ORR. Consequently, integrating the density of states associated with the metal 3d states over potential (energy) range around the demarcation line provides information on the density of ‘localized carriers’ involved in the electrocatalytic reactions.

We would like to emphasize the close correlation between the pseudocapacitance responses in the voltammetric responses (figure 3a) and the p-DOS associated with the Ni and Mn 3d states (figure 4a). For example, the two voltammetric features at approximately 0.6 V and 1.3 V vs RHE in LNO ($x = 0$) closely match the two maxima in the Ni 3d p-DOS. This correlation strongly suggests that the surface Ni coordination is consistent with bulk LNO perovskite structure. Similarly, the line shape of the LMO ($x = 1$) pseudocapacitance is consistent with the single asymmetric Mn 3d p-DOS maximum in the potential range relevant to OER.

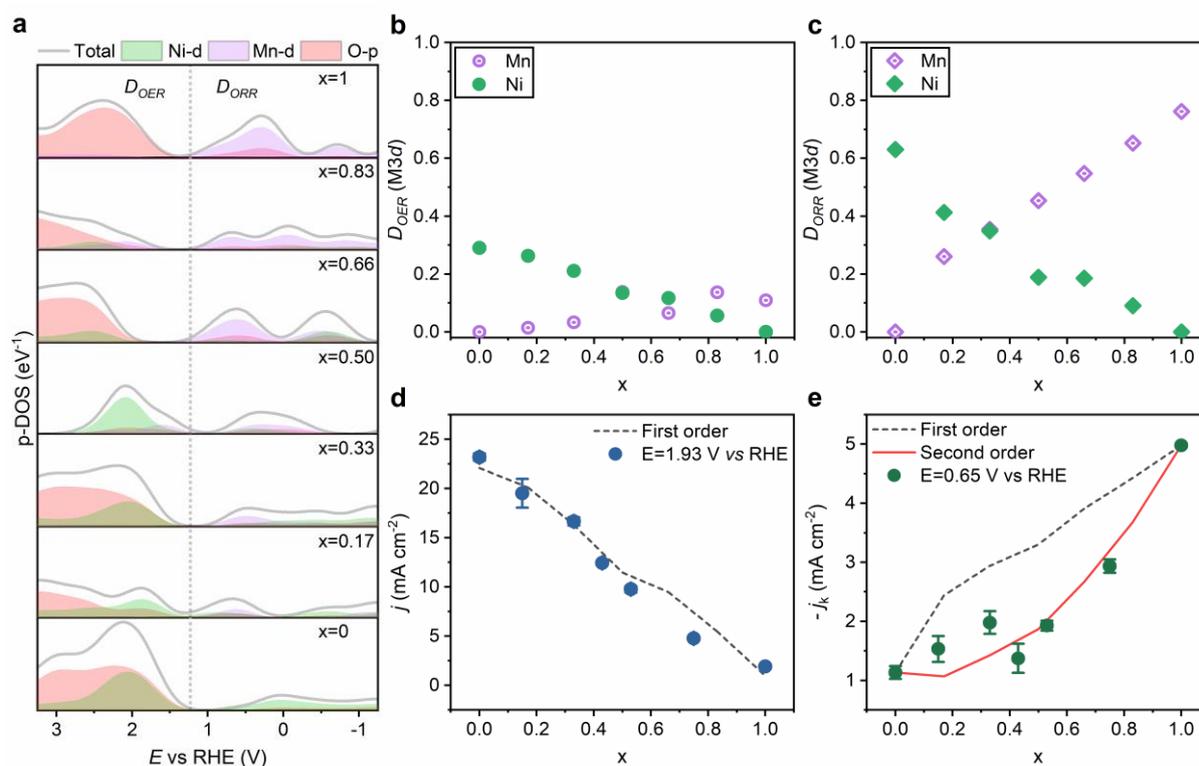


Figure 4. Mn and Ni 3d states determinates oxygen electrocatalysis. (a) Elemental projected DOS in the RHE potential scale for the various LMNO compositions. Dotted line corresponds to 1.23 V vs RHE. (b) DOS associated with metal 3d states normalized by the total density of states in the OER potential range, $D_{OER}(M3d)$, as defined by eq. 1. (c) fraction of DOS metal 3d states in the ORR potential range, $D_{ORR}(M3d)$, as defined by eq. 2. (d) Composition dependence of the OER current density extracted for experimental data at 1.93 V vs RHE and from the first order independent active site model described by eq. 3. (e) Composition dependence of the kinetically limited ORR current at 0.65V vs RHE, in comparison to the trends expected for a first and second order (eq. 4) independent active site model.

Figures 4b and **4c** contrast the relative contributions of Ni and Mn 3d states to the p-DOS within a potential range (ΔE) around 1.23 V, which can be defined in terms of the integral of occupied (D_{occ}) and unoccupied DOS (D_{unocc}) normalised by the total p-DOS:

$$D_{OER}(M3d) = \frac{\int_{1.23}^{1.23+\Delta E} D_{occ}(M3d) \times dE}{\int_{1.23}^{1.23+\Delta E} D_{occ}(M3d+O2p) \times dE} \quad \text{Eq. 1}$$

$$D_{ORR}(M3d) = \frac{\int_{1.23-\Delta E}^{1.23} D_{unocc}(M3d) \times dE}{\int_{1.23-\Delta E}^{1.23} D_{unocc}(M3d+O2p) \times dE} \quad \text{Eq. 2}$$

Although the values of D_{ORR} and D_{OER} may depend on ΔE , the trends show in **Figures 4b** and **4c** are rather independent of the integration range. We can clearly see that the overall contributions of metal 3d states are significantly larger in D_{ORR} in relation to D_{OER} , with the latter mainly dominated by O 2p orbitals. In order to link this picture to the electrochemical activity of the nanostructures, the surface composition of the material should reflect the bulk composition. XPS analysis (**Figure S7**) reveals that the relative surface composition of Mn and Ni varies linearly with the bulk composition, strongly suggesting that no substantial segregation of either element occurs at the surface.

Figure 4d, the current density for the OER at 1.93 V can be simply described as a linearly dependent of the DOS integral of Ni and Mn 3d states as estimated from eq. 2,

$$j(1.93V) = k(\text{Ni}) \times D_{OER}(\text{Ni}) + k(\text{Mn}) \times D_{OER}(\text{Mn}) \quad \text{Eq. 3}$$

The underlying assumption in eq 3 establishes that oxygen evolution is triggered *independently* by unoccupied orbitals (*holes*) at Ni and Mn sites. The OER current at 1.93 V vs RHE can be described in terms of the first phenomenological rate constants values of $k(\text{Ni})=77.0$ and $k(\text{Mn})=10.0$ mA cm⁻², respectively. The dimensions of these constants, which are directly estimated from the experimental values for $x = 0$ and $x = 1$, reflect the fact that we are using fractions rather than total DOS values of the corresponding orbitals. Despite the assumptions involved in the analysis, it is rather remarkable that a close correlation between experimental and calculated responses can be obtained without any fitting parameter.

The composition dependence of the kinetically limited ORR current in **Figure 4e** shows a significantly different to the one observed for OER. Employing first-order kinetics, as described in eq. 3, substantially overestimated the experimental current values. On the other hand, a close correlation can be obtained considering a second-order dependence on $D_{ORR}(M)$

$$j(0.65V) = k'(\text{Ni}) \times [D_{ORR}(\text{Ni})]^2 + k'(\text{Mn}) \times [D_{ORR}(\text{Mn})]^2 \quad \text{Eq. 4}$$

with phenomenological rate constant values of $k'(\text{Ni})=2.85$ and $k'(\text{Mn})=8.60$ and mA cm⁻². Although the ORR and OER kinetic parameters cannot be directly compared as the reactions have different orders with respect to the 'localized carriers', these values allow contrasting the intrinsic activity of Mn and Ni sites. The same composition trends of OER (**Figure 4d**) and ORR (**Figure 4e**) currents are consistently observed at other potentials. It should be mentioned that the direct participation of carriers occupying lattice O 2p states cannot be completely excluded from the electron transfer process. However, the strong correlations displayed in **Figures 4d** and **4e** support our hypothesis that electron transfer dynamics are dominated by metal 3d states.

As far as we are aware, the second-order dependence of ORR kinetics on the electron density at Mn and Ni 3d states is an unprecedented observation with important implications in our understanding of the ORR mechanism at these complex materials. Our current hypothesis is based on the so-called 'bridge' O₂ adsorption, which resembles the mechanism proposed for bi-metallic complexes.³⁸⁻⁴⁰ We propose that the rate determining step involves populating D_{ORR} (M3d) sites, leading to the desorption of OH⁻ groups from adjacent sites and the 'bridge' adsorption of dissolved O₂. This mechanism is consistent with our previous studies in which a quadratic dependence of ORR kinetics with the density of Mn³⁺ sites was observed in La_xBa_{1-x}MnO₃ electrodes.⁴¹

The implications of our findings with regards to establishing activity descriptors for oxygen electrocatalysis are highly significant. The two fundamental guiding principles extracted from our work are:

- 1- A strong overlap in the energy scale between occupied (unoccupied) DOS in highly electron correlated systems with the density of molecular oxygen states in solution is key to promoting ORR (OER), in agreement with the Gerischer model for electron transfer.
- 2- Electrocatalytic activity is dominated by metallic 3d states.

Our results suggest that O 2p states in the perovskite lattice has a negligible contribution to promoting oxygen bond breaking or coupling, in comparison with the cation 3d states. Indeed, as shown in **Figure 4**, LMO is catalytically poor towards OER not only because the phenomenological rate constant on Mn site is 7 times smaller than on Ni sites, but also due to the small contribution of Mn 3d-states to D_{OER} . On the other hand, the ORR kinetics is even more sensitive to the contributions of metal 3d-states in view of the second-order dependence on electron density. Indeed, introducing a small fraction of Mn sites have a significant influence on the rate and selectivity of ORR, with $x = 0.15$ showing the best performance as oxygen bifunctional electrocatalysts.

Finally, we conclude that although parameters such as oxygen binding energy,^{17, 18} metal-oxygen bond hybridization,^{11, 12} and formation energy of oxygen vacancies^{4, 14} are determined by the electronic structure of transition metal oxides, none of them entirely encapsulates the complexity of oxygen electrocatalysis. For example, our DFT calculations do show a decrease in the formation energy of oxygen vacancies (see **Figure S8**) with decreasing Mn content. However, the electronic configuration obtained from DFT is significantly different from the operational conditions, with the E_f under OER conditions located several eV below the calculated value. These studies demonstrate that conducting detailed electrochemical analysis of strongly electron correlated materials, supported by accurate DFT calculations, can allow identifying the key electronic orbitals dictating the electrochemical kinetics. Naturally, the development of a first-principles computational framework that allows accurate estimation of electronic energy levels alignment at electrochemical junctions will be crucial a step towards a comprehensive predicting tool for screening electrocatalysts *in-silico*. Although, important advances have been made in this direction,^{42, 43} this goal remains extremely challenging when considering complex multicomponent materials.

Associated content

Supporting information

The Supporting Information is available free of charge at: <https://>

Material synthesis, experimental details, computational methods; structural and composition analysis featuring Rietveld refinement, XANES, EXFAS, XPS, TEM – EDX; Koutecky-Levich analysis; oxygen vacancy formation energy as a function of material composition. Videos illustrating the 120 atom supercell used for DFT calculations is also provided in the supporting information.

All the data presented in this paper can be freely accessed from the Bristol's Research Data Repository at <https://>

Author contributions

MA, BH and JS equally contributed to this work.

Notes

The authors declare no competing interests.

Acknowledgements

MA acknowledges the financial support from the Saudi Ministry of Education. BH is indebted by the financial support from the EPSRC Centre for Doctoral Training in Catalysis (EP/P016405/1). JS and DJF are thankful for the financial support provided by Johnson Matthey. The authors are grateful to Diamond Light Source for the access to the B18 beamline (SP10306). DT and DJF are grateful for the access to the high-performance computational facilities of the Advanced Computing Research Centre, University of Bristol - <http://www.bris.ac.uk/acrc/>. DT and DJF also acknowledge the support from EPSRC through the grants EP/V008692/1 and EP/V008676/1. The authors also acknowledge the EPSRC support via the capital grant EP/K035746/1, which contributed to the Electron Microscopy tools. XPS analysis was performed at the Bristol University NanoESCA Laboratory (Brunel).

References

- (1) Roger, I.; Shipman, M. A.; Symes, M. D. Earth-Abundant Catalysts for Electrochemical and Photoelectrochemical Water Splitting. *Nat. Rev. Chem.* **2017**, *1* (1), 1-13.
- (2) Stamenkovic, V. R.; Strmcnik, D.; Lopes, P. P.; Markovic, N. M. Energy and Fuels from Electrochemical Interfaces. *Nat. Mater.* **2017**, *16* (1), 57-69.
- (3) Song, J.; Wei, C.; Huang, Z.-F.; Liu, C.; Zeng, L.; Wang, X.; Xu, Z. J. A Review on Fundamentals for Designing Oxygen Evolution Electrocatalysts. *Chem. Soc. Rev.* **2020**, *49* (7), 2196-2214.
- (4) Cheng, X.; Fabbri, E.; Yamashita, Y.; Castelli, I. E.; Kim, B.; Uchida, M.; Haumont, R.; Puente-Orench, I.; Schmidt, T. J. Oxygen Evolution Reaction on Perovskites: A Multieffect Descriptor Study Combining Experimental and Theoretical Methods. *ACS Catal.* **2018**, *8* (10), 9567-9578.
- (5) Li, H.; Kelly, S.; Guevarra, D.; Wang, Z.; Wang, Y.; Haber, J. A.; Anand, M.; Gunasooriya, G. T. K.; Abraham, C. S.; Vijay, S.; Gregoire, J. M.; Nørskov, J. K. Analysis of the Limitations in the Oxygen Reduction Activity of Transition Metal Oxide Surfaces. *Nat. Catal.* **2021**, *4* (6), 463-468.
- (6) Kim, N.-I.; Sa, Y. J.; Yoo, T. S.; Choi, S. R.; Afzal, R. A.; Choi, T.; Seo, Y.-S.; Lee, K.-S.; Hwang, J. Y.; Choi, W. S.; Joo, S. H.; Park, J.-Y. Oxygen-Deficient Triple Perovskites as Highly Active and Durable Bifunctional Electrocatalysts for Oxygen Electrode Reactions. *Sci. Adv.* **2018**, *4* (6), 1-10.

- (7) Hwang, J.; Rao, R. R.; Giordano, L.; Katayama, Y.; Yu, Y.; Shao-Horn, Y. Perovskites in Catalysis and Electrocatalysis. *Science* **2017**, *358* (6364), 751-756.
- (8) Hong, W. T.; Risch, M.; Stoerzinger, K. A.; Grimaud, A.; Suntivich, J.; Shao-Horn, Y. Toward the Rational Design of Non-Precious Transition Metal Oxides for Oxygen Electrocatalysis. *Energy Environ. Sci.* **2015**, *8* (5), 1404-1427.
- (9) Suntivich, J.; May, K. J.; Gasteiger, H. A.; Goodenough, J. B.; Shao-Horn, Y. A Perovskite Oxide Optimized for Oxygen Evolution Catalysis from Molecular Orbital Principles. *Science* **2011**, *334* (6061), 1383-1385.
- (10) Suntivich, J.; Gasteiger, H. A.; Yabuuchi, N.; Nakanishi, H.; Goodenough, J. B.; Shao-Horn, Y. Design Principles for Oxygen-Reduction Activity on Perovskite Oxide Catalysts for Fuel Cells and Metal–Air Batteries. *Nat. Chem.* **2011**, *3* (7), 546-550.
- (11) Hong, W. T.; Stoerzinger, K. A.; Lee, Y.-L.; Giordano, L.; Grimaud, A.; Johnson, A. M.; Hwang, J.; Crumlin, E. J.; Yang, W.; Shao-Horn, Y. Charge-Transfer-Energy-Dependent Oxygen Evolution Reaction Mechanisms for Perovskite Oxides. *Energy Environ. Sci.* **2017**, *10* (10), 2190-2200.
- (12) Li, H.; Sun, S.; Xi, S.; Chen, Y.; Wang, T.; Du, Y.; Sherburne, M.; Ager, J. W.; Fisher, A. C.; Xu, Z. J. Metal–Oxygen Hybridization Determined Activity in Spinel-Based Oxygen Evolution Catalysts: A Case Study of $\text{ZnFe}_{2-x}\text{Cr}_x\text{O}_4$. *Chem. Mater.* **2018**, *30* (19), 6839-6848.
- (13) Hu, C.; Wang, X.; Yao, T.; Gao, T.; Han, J.; Zhang, X.; Zhang, Y.; Xu, P.; Song, B. Enhanced Electrocatalytic Oxygen Evolution Activity by Tuning Both the Oxygen Vacancy and Orbital Occupancy of B-Site Metal Cation in NdNiO_3 . *Adv. Funct. Mater.* **2019**, *29* (30), 1902449.
- (14) Marelli, E.; Gazquez, J.; Poghosyan, E.; Müller, E.; Gawryluk, D. J.; Pomjakushina, E.; Sheptyakov, D.; Piamonteze, C.; Aegerter, D.; Schmidt, T. J.; Medarde, M.; Fabbri, E. Correlation between Oxygen Vacancies and Oxygen Evolution Reaction Activity for a Model Electrode: $\text{PrBaCo}_2\text{O}_{5+\delta}$. *Angew. Chem. Int. Ed.* **2021**, *60* (26), 14609-14619.
- (15) Porokhin, S. V.; Nikitina, V. A.; Aksyonov, D. A.; Filimonov, D. S.; Pazhetnov, E. M.; Mikheev, I. V.; Abakumov, A. M. Mixed-Cation Perovskite $\text{La}_{0.6}\text{Ca}_{0.4}\text{Fe}_{0.7}\text{Ni}_{0.3}\text{O}_{2.9}$ as a Stable and Efficient Catalyst for the Oxygen Evolution Reaction. *ACS Catal.* **2021**, *11* (13), 8338-8348.
- (16) Celorrio, V.; Tiwari, D.; Fermin, D. J. Composition-Dependent Reactivity of $\text{Ba}_{0.5}\text{Sr}_{0.5}\text{Co}_x\text{Fe}_{1-x}\text{O}_{3-\delta}$ Toward the Oxygen Reduction Reaction. *J. Phys. Chem. C* **2016**, *120* (39), 22291-22297.
- (17) Li, Y.; Cheng, W.; Sui, Z.-J.; Zhou, X.-G.; Chen, D.; Yuan, W.-K.; Zhu, Y.-A. Origin of Chemisorption Energy Scaling Relations over Perovskite Surfaces. *J. Phys. Chem. C* **2019**, *123* (46), 28275-28283.
- (18) Jacobs, R.; Hwang, J.; Shao-Horn, Y.; Morgan, D. Assessing Correlations of Perovskite Catalytic Performance with Electronic Structure Descriptors. *Chem. Mater.* **2019**, *31* (3), 785-797.
- (19) Calvillo, L.; Carraro, F.; Vozniuk, O.; Celorrio, V.; Nodari, L.; Russell, A. E.; Debellis, D.; Fermin, D.; Cavani, F.; Agnoli, S.; Granozzi, G. Insights into the Durability of Co–Fe Spinel Oxygen Evolution Electrocatalysts via Operando Studies of the Catalyst Structure. *J. Mater. Chem. A* **2018**, *6* (16), 7034-7041.
- (20) Yang, Y.; Wang, Y.; Xiong, Y.; Huang, X.; Shen, L.; Huang, R.; Wang, H.; Pastore, J. P.; Yu, S.-H.; Xiao, L.; Brock, J. D.; Zhuang, L.; Abruña, H. D. In Situ X-ray Absorption Spectroscopy of a Synergistic Co–Mn Oxide Catalyst for the Oxygen Reduction Reaction. *J. Am. Chem. Soc.* **2019**, *141* (4), 1463-1466.
- (21) Grumelli, D.; Wiegmann, T.; Barja, S.; Reikowski, F.; Maroun, F.; Allongue, P.; Balajka, J.; Parkinson, G. S.; Diebold, U.; Kern, K.; Magnussen, O. M. Electrochemical Stability of the Reconstructed $\text{Fe}_3\text{O}_4(001)$ Surface. *Angew. Chem. Int. Ed.* **2020**, *59* (49), 21904-21908.
- (22) Mefford, J. T.; Akbashev, A. R.; Kang, M.; Bentley, C. L.; Gent, W. E.; Deng, H. D.; Alsem, D. H.; Yu, Y.-S.; Salmon, N. J.; Shapiro, D. A.; Unwin, P. R.; Chueh, W. C. Correlative Operando Microscopy of Oxygen Evolution Electrocatalysts. *Nature* **2021**, *593* (7857), 67-73.
- (23) Gerischer, H. Electron-Transfer Kinetics of Redox Reactions at the Semiconductor/Electrolyte Contact. A New Approach. *J. Phys. Chem* **1991**, *95* (3), 1356-1359.
- (24) Celorrio, V.; Tiwari, D.; Calvillo, L.; Leach, A.; Huang, H.; Granozzi, G.; Alonso, J. A.; Aguadero, A.; Pinacca, R. M.; Russell, A. E.; Fermin, D. J. Electrocatalytic Site Activity Enhancement via Orbital

Overlap in A_2MnRuO_7 ($A = Dy^{3+}$, Ho^{3+} , and Er^{3+}) Pyrochlore Nanostructures. *ACS Appl. Energy Mater.* **2021**, *4* (1), 176-185.

(25) Celorrio, V.; Leach, A. S.; Huang, H.; Hayama, S.; Freeman, A.; Inwood, D. W.; Fermin, D. J.; Russell, A. E. Relationship between Mn Oxidation State Changes and Oxygen Reduction Activity in $(La,Ca)MnO_3$ as Probed by In Situ XAS and XES. *ACS Catal.* **2021**, *11* (11), 6431-6439.

(26) Bradley, K.; Giagloglou, K.; Hayden, B. E.; Jungius, H.; Vian, C. Reversible Perovskite Electrocatalysts for Oxygen Reduction/Oxygen Evolution. *Chem. Sci.* **2019**, *10* (17), 4609-4617.

(27) Tong, Y.; Wu, J.; Chen, P.; Liu, H.; Chu, W.; Wu, C.; Xie, Y. Vibronic Superexchange in Double Perovskite Electrocatalyst for Efficient Electrocatalytic Oxygen Evolution. *J. Am. Chem. Soc.* **2018**, *140* (36), 11165-11169.

(28) García-Muñoz, J. L.; Rodríguez-Carvajal, J.; Lacorre, P.; Torrance, J. B. Neutron-Diffraction Study of $RNiO_3$ ($R=La,Pr,Nd,Sm$): Electronically Induced Structural Changes Across the Metal-Insulator Transition. *Phys. Rev. B* **1992**, *46* (8), 4414-4425.

(29) Blasco, J.; Sánchez, M. C.; Pérez-Cacho, J.; García, J.; Subías, G.; Campo, J. Synthesis and Structural Study of $LaNi_{1-x}Mn_xO_{3+\delta}$ Perovskites. *J. Phys. Chem. Solids* **2002**, *63* (5), 781-792.

(30) Haaß, F. Zur Defektstruktur von Strontium-und Kupferdotiertem Lanthanmanganat. Ph.D. Thesis, Technische Universität Darmstadt, Aachen, Germany, 2005.

(31) Croft, M.; Sills, D.; Greenblatt, M.; Lee, C.; Cheong, S. W.; Ramanujachary, K. V.; Tran, D. Systematic Mn d-Configuration Change in the $La_{1-x}Ca_xMnO_3$ System: A Mn K-Edge XAS Study. *Phys. Rev. B* **1997**, *55* (14), 8726-8732.

(32) Morales, D. M.; Villalobos, J.; Kazakova, M. A.; Xiao, J.; Risch, M. Nafion-Induced Reduction of Manganese and its Impact on the Electrocatalytic Properties of a Highly Active MnFeNi Oxide for Bifunctional Oxygen Conversion. *ChemElectroChem* **2021**, *8* (15), 2979-2983.

(33) Kuznetsov, D. A.; Han, B.; Yu, Y.; Rao, R. R.; Hwang, J.; Román-Leshkov, Y.; Shao-Horn, Y. Tuning Redox Transitions via Inductive Effect in Metal Oxides and Complexes, and Implications in Oxygen Electrocatalysis. *Joule* **2018**, *2* (2), 225-244.

(34) Wang, L.; Adiga, P.; Zhao, J.; Samarakoon, W. S.; Stoerzinger, K. A.; Spurgeon, S. R.; Matthews, B. E.; Bowden, M. E.; Sushko, P. V.; Kaspar, T. C.; Sterbinsky, G. E.; Heald, S. M.; Wang, H.; Wangoh, L. W.; Wu, J.; Guo, E.-J.; Qian, H.; Wang, J.; Varga, T.; Thevuthasan, S.; Feng, Z.; Yang, W.; Du, Y.; Chambers, S. A. Understanding the Electronic Structure Evolution of Epitaxial $LaNi_{1-x}Fe_xO_3$ Thin Films for Water Oxidation. *Nano Lett.* **2021**, *21* (19), 8324-8331.

(35) Celorrio, V.; Calvillo, L.; Dann, E.; Granozzi, G.; Aguadero, A.; Kramer, D.; Russell, A. E.; Fermín, D. J. Oxygen Reduction Reaction at $La_xCa_{1-x}MnO_3$ Nanostructures: Interplay between A-Site Segregation and B-Site Valency. *Catal. Sci. Technol.* **2016**, *6* (19), 7231-7238.

(36) Celorrio, V.; Calvillo, L.; van den Bosch, C. A. M.; Granozzi, G.; Aguadero, A.; Russell, A. E.; Fermin, D. J. Mean Intrinsic Activity of Single Mn Sites at $LaMnO_3$ Nanoparticles Towards the Oxygen Reduction Reaction. *ChemElectroChem* **2018**, *5* (20), 3044-3051.

(37) Costentin, C.; Porter, T. R.; Savéant, J.-M. Nature of Electronic Conduction in "Pseudocapacitive" Films: Transition from the Insulator State to Band-Conduction. *ACS Appl. Mater. Interfaces* **2019**, *11* (32), 28769-28773.

(38) Goldstein, J. R.; Tseung, A. C. C. A Joint Pseudo-Splitting/Peroxide Mechanism for Oxygen Reduction at Fuel Cell Cathodes. *Nature* **1969**, *222* (5196), 869-870.

(39) Yeager, E. Electrocatalysts for O_2 Reduction. *Electrochim. Acta* **1984**, *29* (11), 1527-1537.

(40) Risch, M. Perovskite Electrocatalysts for the Oxygen Reduction Reaction in Alkaline Media. *Catalysts* **2017**, *7* (5), 1-31.

(41) Gobaille-Shaw, G. P. A.; Celorrio, V.; Calvillo, L.; Morris, L. J.; Granozzi, G.; Fermín, D. J. Effect of Ba Content on the Activity of $La_{1-x}Ba_xMnO_3$ Towards the Oxygen Reduction Reaction. *ChemElectroChem* **2018**, *5* (14), 1922-1927.

(42) Cheng, J.; Sprik, M. Alignment of Electronic Energy Levels at Electrochemical Interfaces. *Phys. Chem. Chem. Phys.* **2012**, *14* (32), 11245-11267.

(43) Le, J.-B.; Chen, A.; Li, L.; Xiong, J.-F.; Lan, J.; Liu, Y.-P.; Iannuzzi, M.; Cheng, J. Modeling Electrified Pt(111)-H_{ad}/Water Interfaces from Ab Initio Molecular Dynamics. *JACS Au* **2021**, *1* (5), 569-577.