

# Northumbria Research Link

Citation: Li, Weina, Li, Jiaqi, Wen, Jiahao, Wen, Ming, Chen, Shiwei, Wu, Qingsheng and Fu, Richard (2019) Hollow nanostructure of sea-sponge-C/SiC@SiC/C for stable Li<sup>+</sup>-storage capability. Science Bulletin, 64 (16). pp. 1152-1157. ISSN 2095-9273

Published by: Elsevier

URL: <https://doi.org/10.1016/j.scib.2019.06.014>  
<<https://doi.org/10.1016/j.scib.2019.06.014>>

This version was downloaded from Northumbria Research Link:  
<http://nrl.northumbria.ac.uk/id/eprint/39733/>

Northumbria University has developed Northumbria Research Link (NRL) to enable users to access the University's research output. Copyright © and moral rights for items on NRL are retained by the individual author(s) and/or other copyright owners. Single copies of full items can be reproduced, displayed or performed, and given to third parties in any format or medium for personal research or study, educational, or not-for-profit purposes without prior permission or charge, provided the authors, title and full bibliographic details are given, as well as a hyperlink and/or URL to the original metadata page. The content must not be changed in any way. Full items must not be sold commercially in any format or medium without formal permission of the copyright holder. The full policy is available online: <http://nrl.northumbria.ac.uk/policies.html>

This document may differ from the final, published version of the research and has been made available online in accordance with publisher policies. To read and/or cite from the published version of the research, please visit the publisher's website (a subscription may be required.)



**Northumbria  
University**  
NEWCASTLE



**UniversityLibrary**

## Accepted Manuscript

### Article

Hollow nanostructure of sea-sponge-C/SiC@SiC/C for stable Li<sup>+</sup>-storage capability

Weina Li, Jiaqi Li, Jiahao Wen, Ming Wen, Shiwei Chen, Qingsheng Wu, Yongqing Fu

PII: S2095-9273(19)30339-1  
DOI: <https://doi.org/10.1016/j.scib.2019.06.014>  
Reference: SCIB 735

To appear in: *Science Bulletin*

Received Date: 18 March 2019  
Revised Date: 30 April 2019  
Accepted Date: 3 June 2019

Please cite this article as: W. Li, J. Li, J. Wen, M. Wen, S. Chen, Q. Wu, Y. Fu, Hollow nanostructure of sea-sponge-C/SiC@SiC/C for stable Li<sup>+</sup>-storage capability, *Science Bulletin* (2019), doi: <https://doi.org/10.1016/j.scib.2019.06.014>

This is a PDF file of an unedited manuscript that has been accepted for publication. As a service to our customers we are providing this early version of the manuscript. The manuscript will undergo copyediting, typesetting, and review of the resulting proof before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.



Received 18-March-2019; Revised 30-April-2019; Accepted 03-June-2019

## Hollow nanostructure of sea-sponge-C/SiC@SiC/C for stable Li<sup>+</sup>-storage capability

Weina Li,<sup>†,a</sup> Jiaqi Li,<sup>†,a</sup> Jiahao Wen,<sup>b</sup> Ming Wen,<sup>\*,a</sup> Shipei Chen,<sup>a</sup> Qingsheng Wu,<sup>a</sup>  
Yongqing Fu<sup>c</sup>

<sup>a</sup>School of Chemical Science and Engineering, Shanghai Key Laboratory of Chemical Assessment and Sustainability, Tongji University, Shanghai 200092, China

<sup>b</sup>School of Electrical Engineering, Chongqing University, Chongqing 400044, China

<sup>c</sup>Faculty of Engineering and Environment, Northumbria University, NE1 8ST, UK

Corresponding author: m\_wen@tongji.edu.cn (Ming WEN)

<sup>†</sup>These authors contributed equally to this work.

### KEYWORDS

SiC, Lithium ion batteries, Cycling stability, Sea-sponge-C/SiC@SiC/C

### ABSTRACT

For the purpose of stable performance in energy storage systems, a new hollow nanostructure of sea-sponge-C/SiC@SiC/C (SCS/SiC@SiC/C) has been successfully fabricated by the SCS/SiC nanospheres coated with SiC/C shells through an *in situ* reduction process. Based on SCSs and the carbon shells, the stable hollow structures of SCS/SiC@SiC/C can contain large proportion of active SiC layers, which are adhered to both SCSs and the inner surfaces of carbon shells. Such nanostructured anode enables an excellent cycling stability with a capacity of 612 mAh g<sup>-1</sup> at a current density of 0.5 A/g after 1,800 cycles, achieving an excellent stable Li<sup>+</sup>-storage capability.

## 1. Introduction

The ever-growing requirements for portable electronic devices have accelerated the development of lithium-ion batteries (LIBs) [1]. However, the mostly used anode material for the LIBs, e.g., graphite has a limited practical capacity of 372 mAh/g. Although some materials (e.g., Si) with large theoretical specific capacity were explored for the high energy density, there are still some problems including large volumetric expansion and low electrical conductivity [2-4]. To solve some of these problems, carbon is frequently introduced to fabricate a composite structure to achieve an improved cycling stability and excellent rate performance [5-10]. Silicon carbide (SiC), was previously considered as an inactive material, and only served to improve the structural stability [11]. However, several recent studies have reported the

possibilities of the electrochemically lithiated SiC, which could be used as the electrode material for the LIBs. The chemical reactions of Li and SiC was detected when Li was deposited onto the SiC surface pre-coated by graphene [12]. The growth of graphene on SiC can increase the Li<sup>+</sup>-storage capacity of SiC up to a value which is the double value of the graphite [13]. A bowl-like SiC nanostructure with ultra-thin SiC nanoshells encapsulated in hollow graphitic carbon spheres as the LIB anodes displayed unexpectedly high electrochemical performance [14].

However, low electrical conductivity and Li<sup>+</sup> diffusion are still critical issues for the SiC anode materials. Herein, we have proposed hollow nanospheres of sea-sponge-C/SiC@SiC/C (SCS/SiC@SiC/C) for the excellent Li<sup>+</sup>-storage capability. Such the new design has the following advantages: (1) the stable nanostructure contains numerous inner interconnected-channels, not only can withstand large stresses caused by the volume changes of SiC, but also is beneficial for infiltration of the electrolyte and Li<sup>+</sup> diffusion; (2) besides improve the conductivity, the SCSs also contribute the growth of an intimately contacted SiC layer on surface, meanwhile the diffusion passway of Li<sup>+</sup> is greatly shortened; (3) owing to the lower volume expansion compare to Si, SiC could avoid the drawback of volume expansion/contraction in repeated cycling, pulverization and loss of electronic contact. Furthermore, the stable SiC can work as a scaffold to withstand the stresses induced from volume changes for the formation of a stable SEI, which may contribute to superior cycling stability; (4) the cycling performance of the SCS/SiC@SiC/C

composite can be effectively improved compare to those of the SCS/SiC nanospheres, because the SiC/C shells can contribute to the increase of capacity and help to prevent the side reactions during charge/discharge processes.

In this work, the hollow nanostructure of SCS/SiC@SiC/C was successfully synthesized through an *in situ* reduction process [15]. It can exhibit excellent cycling stability when used as the anode material in LIBs. The results show that the capacity keeps increasing after initial 60 cycles, and reach a value of 612 mAh/g after 1,800 cycles at 0.5 A/g. Its exceptionally long cycle stability is due to the formation of stable structures of interconnected SCS/SiC mesoporous spheres coated with SiC/C.

## 2. Experimental

### 2.1. Preparation of SCS/SiC@SiC/C composites

Based on previously reported work of SCSs synthesis [16,17], the SCS/SiO<sub>2</sub> spheres were prepared using a modified Stöber's method [18]. Typically, the SCS (30 mg) was dispersed in ethanol solution and ultrasonicated for 15 min. Cetyltrimethylammonium bromide (CTAB) solution (1.0 mL, 10 mM) was added in the above solution under stirring. Then tetraethoxysilane (TEOS, 1.0 mL) and aqueous ammonia solution (1.0 mL) were sequentially added and continuously stirred for 1.0 h. The product was collected by centrifugation and washed with water and ethanol. Then the prepared SCS/SiO<sub>2</sub> (80 mg) was dissolved into ethanol with CTAB solution (1.0 mL, 10 mmol/L), and stirred for 20 min. Then aqueous ammonia (0.3

mL) and 50 mg resorcinol were added into the above solution to stir 30 min, formaldehyde solution (0.1 mL) was added to kept for 2.0 h. The products were collected by centrifugation, washed by water and ethanol. The as-prepared powders were then transferred into a tubular furnace and heated at 800 °C under Ar for 2.0 h. The obtained SCS/SiO<sub>2</sub> or SCS/SiO<sub>2</sub>@C samples were mixed with Mg powder in a molar ratio of 1:2, and then heated to 800 °C with a heating rate of 20 °C/min in a tube furnace under Ar for 2 h. The resultant products were then carefully dispersed in a 0.5 M HCl solution under stirring for 2 h and dispersed in 1% HF aqueous solution for 30 min to remove the byproducts and impurities. The final object products of SCS/SiC and SCS/SiC@SiC/C were washed with the deionized water for three times and dried at 70 °C in a vacuum oven for 24 h.

## 2.2. Characterizations

Morphologies and structures of the samples were characterized using a field emission scanning electron microscope (FE-SEM, JEOL, S-4800), a high resolution transmission electron microscope (HR-TEM, JEOL, JEM-2100EX) with selective area electron diffraction (SAED), X-ray diffraction (XRD, Bruker, D8 Advance) with Cu K $\alpha$  radiation ( $\lambda = 0.154056$  nm). Elemental mapping was carried out on energy disperse X-ray spectroscopy (EDS, Oxford, TN-5400). The molecular structure was characterized by Fourier transform infrared spectroscopy (FT-IR, Thermo, NEXUS), Raman spectra (Renishaw, inVia). The chemical bond information was analyzed by X-ray photoelectron spectroscopy (XPS, Perkin Elmer, PHI-5000C ESCA) with Mg

K $\alpha$  radiation. Binding energy of the elements was calibrated using the containment carbon (C 1s =284.6 eV) and analyzed using the XPS Peak 41. Weight loss was measured on thermo gravimetric analyzer (TGA, Netzsch, STA409PC). The specific surface area was investigated by adsorption isotherm of nitrogen (Micrometrics, ASAP2020), using the Brunauer-Emmett-Teller (BET) method.

### 2.3. Electrochemical measurements



Electrochemical measurements were performed using CR2016 coin-type cells assembled in an argon-filled glove box. To prepare the working electrodes, active materials were mixed with conductive carbon black and polyvinylidene fluoride (PVDF) binder (dissolved in *N*-methyl pyrrolidone) with a mass ratio of 7:2:1, the resulting slurry was uniformly casted onto a copper foil and dried overnight in a vacuum oven at 100 °C. Subsequently, the coated copper foil was punched into wafers with a diameter of 15 mm. The mass loading of the electrode was  $1.5 \pm 0.1$  mg/cm<sup>2</sup>. Then the coin cells were assembled with active materials as the anode, metallic lithium foil as the cathode, and glass fiber as separator. The electrolyte was a solution of LiPF<sub>6</sub> dissolved in mixed solvent of ethylene carbonate (EC) and dimethyl carbonate (DMC) (1:1 by volume). Galvanostatic electrochemical experiments were conducted using a multichannel battery test system (LAND CT2000A) at 25 °C. Cyclic voltammetry (CV, 0.1 mV/s) and electrochemical impedance spectroscopy (EIS, 100 kHz–0.01 Hz, 10 mV) measurements were conducted using an electrochemical workstation (Princeton Applied Research Versa STAT4). The



specific capacities of all the samples were calculated based on the total mass of active materials.

### 3. Results and discussion

Fig. 1a presents a schematic illustration of fabrication processes of the SCS/SiC@SiC/C nanocomposite based on SCSs (Fig. S1a online). Firstly, SCS/SiO<sub>2</sub> (Fig. S1b online) was prepared by evenly dispersing a layer of SiO<sub>2</sub> onto SCSs. Then, SCS/SiO<sub>2</sub> was encapsulated in a carbon layer to form SCS/SiO<sub>2</sub>@C (Fig. S1c online) by coating a layer of resorcinol-formaldehyde shell which was transformed to carbon in the carbonization process at 800 °C for 3 h. With the assistance of Mg (which has a boiling point of = ~650 °C) during the magnesiothermic reduction reaction, the layer of SiO<sub>2</sub> in SCS/SiO<sub>2</sub> reacted with SCS to produce SiC, while SiO<sub>2</sub> could react with both the inner SCS and the carbon shell in SCS/SiO<sub>2</sub>@C. According to the following reactions [19]:



The kinetics behind magnesiothermic reduction process were previously investigated for the production of both Si [20] and SiC [21-23] as anode of LIBs. It is believed that the SiO<sub>2</sub> is reduced to Mg<sub>2</sub>Si which is then served as the intermediates and will form SiC when the Mg<sub>2</sub>Si encounters carbon through a solid state diffusion [24]. Larger contact area between SiO<sub>2</sub> and C, higher

heating rate and higher reaction temperature are favorable for the formation of SiC. The mechanism is shown in the inset of Fig. 1b. During the reduction process, all the parameters were carefully controlled to facilitate the formation of cubic SiC while to avoid the formation of Si. These parameters include: a high molar ratio of Mg:SCS/SiO<sub>2</sub>@C of 2:1, a fast heating rate of 20 °C/min, a higher reaction temperature of 800 °C. Finally, a mixture of SCS/SiC or SCS/SiC@SiC/C, magnesium oxide and residual silica were obtained. Magnesium oxide and the remaining silica were completely washed away by the HCl and HF diluted aqueous solutions.

**Fig. 1.** (Color online) (a) The fabrication scheme of SCS/SiC@SiC/C nanospheres. (b) SiC formed by magnesiothermic reduction. (c) 2D cross-section view of the lithiation and delithiation process. (d)–(l) SEM, TEM, HRTEM images with inset crystal lattice spacing, SAED, XRD, EDS, Elemental mapping images of SCS/SiC spheres. (m)–(o) SEM and TEM images of SCS/SiC@SiC/C spheres.

From the SEM and TEM images of SCS/SiC in Fig. 1d–f, the layer of SiC is well-distributed on the surface of SCSs and has a good contact among each other. Such a structure has a lot of inner spaces to allow the volume changes of active material for lithiation/delithiation processes. The *in-situ* growth of the SiC layer ensures its good contact with SCSs, and enable SCS/SiC to perfectly remain in the sea-sponge-shapes (Fig. S1d online). The XRD pattern of the SCS/SiC shows several diffraction peaks at  $2\theta=35.6^\circ$ ,  $60.0^\circ$ ,  $71.8^\circ$ , which are identified as those from the cubic( $\beta$ )-SiC phase (JCPDS No. 29-1129) (Fig. 1i

(top)). The formation of crystalline SiC layer can be proved by the HR-TEM image and the corresponding SAED patterns. The lattice constant obtained from the HR-TEM image is 0.25 nm, which is the same with the (111) lattice face of a cubic SiC (Fig. 1g), and confirmed by the SAED pattern (Fig. 1h). EDS analysis (Fig. 1i (bottom)) reveals that the sample is composed of only silicon and carbon. It should be noted that there isn't any Mg (or magnesium oxide) signal detected, indicating the by-products of MgO formed in the magnesiothermic reduction process was successfully removed. Fig. 1j-l shows the comprehensive mapping image for C and Si elements overlapped with corresponding SEM image of SCS/SiC sample. The individual mappings of Si and C indicate the uniform distribution of SiC on the SCSs. Fig. 1m-o shows the SEM and TEM images of the SCS/SiC@SiC/C nanocomposite, which have an ordered inner hollow spherical structure with diameters ranging from 0.8 to 2.2  $\mu\text{m}$ . Both of them retain the morphology of the SCSs without apparent changes even after the magnesiothermic reduction process and treatment with HCl and HF solutions. Such nanostructures can increase the chance of forming the electrochemically active SiC layer through increasing the contact areas with C to ensure a good electronic conductivity, which could enable the long-cycle stability for the  $\text{Li}^+$ -storage capability.

The successful etching of remained  $\text{SiO}_2$  was also proved by checking the FT-IR spectra of SCS/SiC@SiC/C before and after the HF treatment. In the FT-

IR spectra (Fig. 2a), two vibration peaks at 475 and 1,111  $\text{cm}^{-1}$  assigned to Si-O bonds disappear after the remaining  $\text{SiO}_2$  was removed [25]. Raman spectra shown in Fig. 2b, illustrate that the D band (electron decoherence in optics and transport phenomena in  $\text{sp}^2$  carbons) and G band ( $E_{2g}$  mode of carbon) were observed at 1,322 and 1594  $\text{cm}^{-1}$ , respectively. The two more peaks at 780 and 940  $\text{cm}^{-1}$  could be assigned to the transverse optical and longitudinal optical of SiC [26], indicating that SCS/SiC and SCS/SiC@SiC/C inherit the highly ordered backbone of the SCS and the ratio of  $I_D/I_G$  is increased due to the formation of more defects on the carbon layer. Fig. 2c shows the TG analysis. It's surprisingly to notice that, unlike SCS/SiC, the weight losses of SCS/SiC@SiC/C, i.e., the burning of carbon, can be divided into two stages, suggesting that there are two different types of carbon materials in the materials, e.g., the inner carbon backbone and the exterior carbon shell. Results show that the free carbon content is 26.6wt% for SCS/SiC and 39.3wt% for SCS/SiC@SiC/C. So both the samples are composites consisting of crystalline SiC and carbon with the mass ratio of SiC is 73.4wt% in SCS/SiC and 60.9 wt% in SCS/SiC@SiC/C, respectively. XPS spectra (Fig. 2d) presents several peaks observed at around 95.5, 151.9, 285.2, 530.0 eV, which can be assigned to Si 2p, Si 2s, C 1s and O 1s, respectively. The survey spectra of SCS/SiC@SiC/C is similar to that of SCS/SiC due to same composition except that the C 1s peak in former is much higher than that of the later, indicating the

formation of C shell. The detailed C 1s peak of SCS/SiC and SCS/SiC@SiC/C are displayed in Fig. 2e, f. The C 1s spectrum of SCS/SiC@SiC/C (Fig. 2f) can be fitted into several peaks which can be ascribed to C=O, carbide bonds from SiC and the different components of carbon bonds, respectively.

**Fig. 2.** (Color online) FT-IR spectra (a), Raman spectra (b), TG analysis (c), XPS full spectra (d), detail analysis of C 1s for SCS/SiC (e) and SCS/SiC@SiC/C (f).

The electrochemical performances were evaluated and shown in Fig. 3. The CVs of SCS/SiC (Fig. 3a) and SCS/SiC@SiC/C (Fig. 3d) anodes for the initial 3 cycles with the potentials ranging from 0.05 to 3V versus Li/Li<sup>+</sup>, which display similar profiles of the lithiation and delithiation processes of SiC. Specifically, there are two humps that are appeared at around 1.0 and 0.7 V in the first reduction process but then disappeared in the next two cycles. This indicates the irreversible reaction as a result of the formation of SEI layer [27]. On the other hand, in the anodic side, the two peaks at about 0.15 and 0.2 V are attributed to the partly reversible delithiation process of SiC [28]. Meanwhile, Fig. 3b and e show the galvanostatic charge/discharge profiles with different cycles at 0.5 A/g for SCS/SiC and SCS/SiC@SiC/C, respectively. There are a couple of slopes instead of the large plateaus of voltage during the first discharge process, which is different from those profiles of silicon but consistent with the previous reports that the fully lithiation of SiC produces Li<sub>x</sub>SiC instead of Li<sub>x</sub>Si. The cross-section view of the lithiation process for

SCS/SiC and SCS/SiC@SiC/C are depicted in Fig. 1c. The impedance values and Nyquist plots of the electrodes are shown in Fig. 3c and f, respectively. The semi-circles that correspond to the charge transfer resistances suggest that the impedance of the SCS/SiC@SiC/C is effectively decreased compared to that of the SCS/SiC due to the carbon shell. On the other hand, the repeated cycling can result in an improved conductivity for both of the electrode materials which suggests a better charge transport after a long-term cycling, and this is consistent with the increasing in capacity that was observed in Fig. 3g. Fig. 3g illustrates the long-term cycling stability of SCS/SiC and SCS/SiC@SiC/C composites at 0.5A/g under the voltage window of 0.01–2.5 V. The cycling performance of the SCSs is also shown in the same figure for comparisons. The SCS/SiC achieved an initial discharge capacity of 1,046.7 mAh/g. Then the capacity was declined until 60 cycles when a minimum value of 352 mAh/g was retained, and after that, the discharge capacity was increased steadily and gained a relatively high capacity of 662 mAh/g after 950 cycles. Fig. S2a (online) presents the cycling behavior of SCS/SiC. The continuously increased capacity is due to the activation process of SiC and the enlarged surface areas caused by microstructural changes during the lithiation/delithiation, which offering more attachment sites and shortened transmission paths for Li<sup>+</sup>. The initial discharge and charge capacities of SCS/SiC@SiC/C are 929.8 and 288.5 mAh/g (Fig. 3g), respectively, which are slightly lower than those of the

SCS/SiC. It can be explained from the higher weight percentage of C in the SCS/SiC@SiC/C sample compared to that in the SCS/SiC, and such amorphous C exhibits less electrochemical activity than SiC. The Coulombic efficiency in the first-cycle was relatively low because the irreversible formation of SEI generated at the carbon layer surface, which consumes more lithium. The profile of cycling performance for SCS/SiC@SiC/C, although resembling that for SCS/SiC, suffers from fast decay in the first 60 cycles. However, it shows a continuously increasing tendency up to almost 2,000 cycles with a capacity value reaching 612 mAh/g. Table S1 clearly demonstrates that the performance of SCS/SiC@SiC/C is more stable than those of the reported materials [22,23,27-29]. The structure of SCS/SiC@SiC/C can be well maintained after the long-term cycling (Fig. S2b online). These results suggested the exceptional structural durability and therefore excellent cycling stability of the SCS/SiC@SiC/C. The rate capabilities were evaluated at various current densities from 0.2 to 2 A/g and shown in Fig. 3h. Both the SCS/SiC and SCS/SiC@SiC/C nanocomposites can deliver stable capacities and then change to a higher capacity when the current density was reverted to 0.2 A/g, suggesting excellent rating performance and structural stability. It is also worthwhile to note that when the current density is increased to 1 and 2 A/g, the SCS/SiC@SiC/C delivered almost the same capacity compared to that of the SCS/SiC. However, the capacity of SCS/SiC@SiC/C is lower than those of

SCS/SiC at 0.2 and 0.5 A/g. When the current density was switched back to 0.2 A/g at the 45th cycle again, the SCS/SiC could deliver a capacity of 480 mAh/g which is even higher than that achieved in the previous cycles. It might be that the high rate lithiation-induced reconstruction process is favorable for a stable SEI layer formation [30]. All the above results demonstrate that the as-obtained hollow nanostructure of SCS/SiC@SiC/C can achieve a good stability for nanostructures and long term cyclability for the LIBs applications.

**Fig. 3.** (Color online) (a), (d) Cyclic voltammograms at a scan rate of 0.1 mV/s. (b), (e) Discharge-charge potential profiles at 0.5 A/g. (c), (f) Nyquist curves. (g) Cycling performances. (h) The rate performances.

#### 4. Conclusions

In conclusion, the *in-situ* magnesiothermic reduction process was carried out to synthesize the new hollow nanostructures of SCS/SiC@SiC/C. The unique architectural advantages combine the conductive SCSs and the mechanically stable hollow structures, the SCS/SiC@SiC/C anode material could enable excellent double stability for rate and cycling in LIBs, suggesting its great potential for electrochemical energy storage and conversion applications.

#### Conflict of interest

The authors declare that they have no conflict of interest.

#### Acknowledgments



This work was supported by the National Natural Science Foundation of China (21771140 and 51771138) and UK Engineering and Physical Sciences Research Council (EPSRC, EP/P018998/1).

### Author contributions

Weina Li and Jiaqi Li contributed to the materials fabrication, characterization, and the electrochemical measurements. Jiahao Wen and Shipei Chen contributed to the data analysis. Ming Wen, Qingsheng Wu and Yongqing Fu contributed to manuscript writing.

### References

- [1] Armand M, Tarascon JM. Building better batteries. *Nature* 2008; 451: 652-657.
- [2] McDowell MT, Lee SW, Cui Y, et al. Understanding the lithiation of silicon and other alloying anodes for lithium-ion batteries. *Adv Mater* 2013; 25: 4966-4985.
- [3] Kong XZ, Zheng YC, Wang YP, et al. Necklace-like Si@C nanofibers as robust anode materials for high performance lithium ion batteries. *Sci Bull* 2019; 64: 261-269.
- [4] Liu N, Lu Z, Zhao J, et al. A pomegranate-inspired nanoscale design for large volume-change lithium battery anodes. *Nat Nanotechnol* 2014; 9: 187-192.
- [5] Sun BL, Wen M, Wu QS, et al. Oriented growth & assembly of Ag@C@Co pentagonalprism nanocables and their highly activity selected catalysis along the edges for dehydrogenation. *Adv Funct Mater* 2012; 22: 2860-2866.
- [6] Zhang R, Du Y, Li D, et al. Highly reversible and large lithium storage in mesoporous Si/C nanocomposite anodes with silicon nanoparticles embedded in a carbon framework. *Adv Mater* 2014; 26: 6749-6755.
- [7] Fang H, Yang JH, Wen M, et al. Nanoalloy materials for chemical catalysis. *Adv Mater* 2018; 30: 1705698.
- [8] Qin RH, Shao GQ, Hou JX, et al. One-pot synthesis of Li<sub>3</sub>VO<sub>4</sub>@C nanofibers by electrospinning with enhanced electrochemical performance for lithium-ion batteries. *Sci Bull* 2017; 62: 1081-1088.
- [9] Yan WX, Wu QN, Wen M, et al. A superior sodium/lithium-ion storage material: sea-sponge-C/Sn<sub>2</sub>Fe@GO. *Inorg Chem*, doi: 10.1021/acs.inorgchem.9b00621.
- [10] Lu Z, Liu N, Lee H, et al. Nonfilling carbon coating of porous silicon micrometer-sized particles for high-performance lithium battery anodes. *ACS Nano* 2015; 9: 2540-2547.

- [11]Chen Z, Zhou M, Cao Y, et al. In situ generation of few-layer graphene coatings on SnO<sub>2</sub>-SiC core-shell nanoparticles for high-performance lithium-ion storage. *Adv Energy Mater* 2012; 2: 95-102.
- [12]Virojanadara C, Watcharinyanon S, Zakharov AA, et al. Epitaxial graphene on 6H-SiC and Li intercalation. *Phys Rev B* 2010; 82: 2460-2468.
- [13] Lipson AL, Chattopadhyay S, Karmel HJ, et al. Enhanced lithiation of doped 6H silicon carbide (0001) via high temperature vacuum growth of epitaxial graphene. *J Phys Chem C* 2012; 116: 20949-20957.
- [14]Li H, Yu H, Zhang X, et al. Bowl-like 3C-SiC nanoshells encapsulated in hollow graphitic carbon spheres for high-rate lithium-ion batteries. *Chem Mater* 2016; 28: 1179-1186.
- [15]Shi Y, Zhang F, Hu Y, et al. Low-temperature pseudomorphic transformation of ordered hierarchical macro-mesoporous SiO<sub>2</sub>/C nanocomposite to SiC via magnesiothermic reduction. *J Am Chem Soc* 2018; 132: 5552-5553.
- [16]Chen SP, Xing K, Wen M, et al. Hierarchical assembly and superior sodium storage properties of a sea-sponge structured C/SnS@C nanocomposite. *J Mater Chem A* 2018; 6: 7631-7638.
- [17] Chen SP, Wu QN, Wen M, et al. Sea-sponge-like structure of nano-Fe<sub>3</sub>O<sub>4</sub> on skeleton-C with long cycle life under high rate for Li-ion batteries. *ACS Appl Mater Interfaces* 2018; 10: 19656-19663.
- [18] Stöber W, Fink A, E. Bohn, et al. Controlled growth of monodisperse silica spheres in the micron size range. *J Colloid Interface Sci* 1968; 26: 62-69.
- [19]Bao Z, Weatherspoon MR, Shian S, et al. Chemical reduction of three-dimensional silica micro-assemblies into microporous silicon replicas. *Nature* 2007; 446: 172-175.
- [20]Richman EK, Kang CB, Brezesinski T, et al. Ordered mesoporous silicon through magnesium reduction of polymer templated silica thin films. *Nano Lett* 2008; 8: 3075-3079.
- [21]Ngo DT, Le HTT, Pham X, et al. Facile synthesis of Si@SiC composite as an anode material for lithium-ion batteries. *ACS Appl Mater Interfaces* 2017; 9: 32790-32800.
- [22]Wen Z, Lu G, Cui S, et al. Rational design of carbon network cross-linked Si-SiC hollow nanosphere as anode of lithium-ion batteries. *Nanoscale* 2014; 6: 342-351.
- [23]Wang C, Li Y, Ostrikov KK, et al. Synthesis of SiC decorated carbonaceous nanorods and its hierarchical composites Si@SiC@C for high-performance lithium ion batteries. *J Alloy Compd* 2015; 646: 966-972.
- [24]Ahn J, Kim HS, Pyo J, et al. Variation in crystalline phases: Controlling the selectivity between silicon and silicon carbide via magnesiothermic reduction using silica/carbon composites. *Chem Mater* 2016; 28: 1526-1536.
- [25]Putz A, Putz M. Spectral inverse quantum (spectral-IQ) method for modeling mesoporous systems: application on silica films by FTIR. *Int J Mol Sci* 2012; 13: 15925-15941.



- [26] Zhuang H, Zhang L, Staedler T, et al. Nanoscale integration of SiC-SiO<sub>2</sub> core-shell nanocables in diamond through a simultaneous hybrid structure fabrication. *Appl Phys Lett* 2012; 100: 193102.
- [27] Chen Z, Cao Y, Qian J, et al. Antimony-coated SiC nanoparticles as stable and high-capacity anode materials for Li-ion batteries. *J Phys Chem C* 2010; 114: 15196-15201.
- [28] Hu Y, Liu X, Zhang X, et al. Bead-curtain shaped SiC@SiO<sub>2</sub> core-shell nanowires with superior electrochemical properties for lithium-ion batteries. *Electrochim Acta* 2016; 190: 33-39.
- [29] Sun XJ, Shao CZ, Zhang F, et al. SiC nanofibers as long-life lithium-ion battery anode materials. *Front Chem* 2018; 6: 166.
- [30] Sun H, Xin G, Hu T, et al. High-rate lithiation-induced reactivation of mesoporous hollow spheres for long-lived lithium-ion batteries. *Nat Commun* 2014; 5: 4526.




**Weina Li** is currently a master candidate in the School of Chemical Science and Engineering, Tongji University. Her research is focus on the synthesis of carbon-based nanomaterials for electrochemical energy storage.




Ming Wen is a full professor in the School of Chemical Science and Engineering at Tongji University. She received her Ph.D. degree in Analysis Chemistry in 2002 from Kinki University in Japan, and International Academic Communication in Tohoku University (Japan) and Humboldt-Universität zu Berlin (German) in 2011 and 2015, respectively. Her scientific interests are focused on metal & alloy catalytic nanomaterials for hydrogen generation, environments treatment, and electrodes nanomaterials.

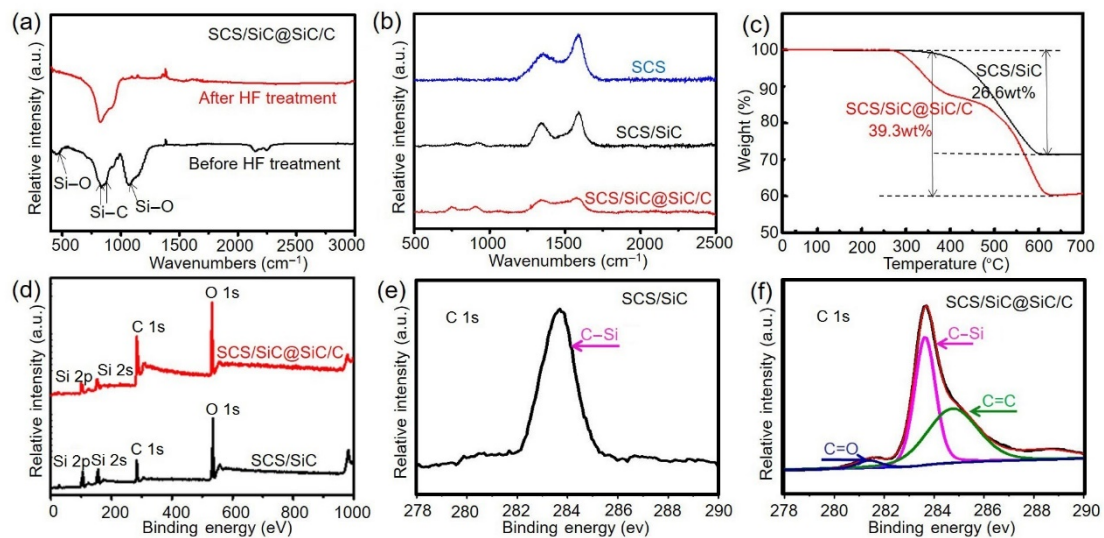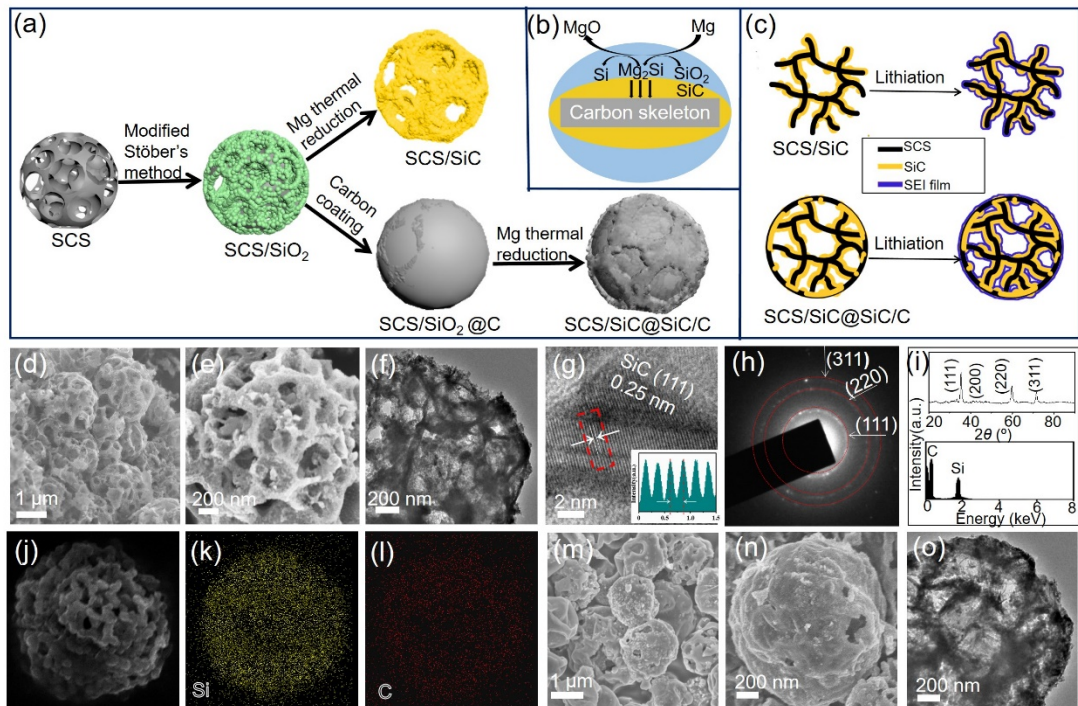

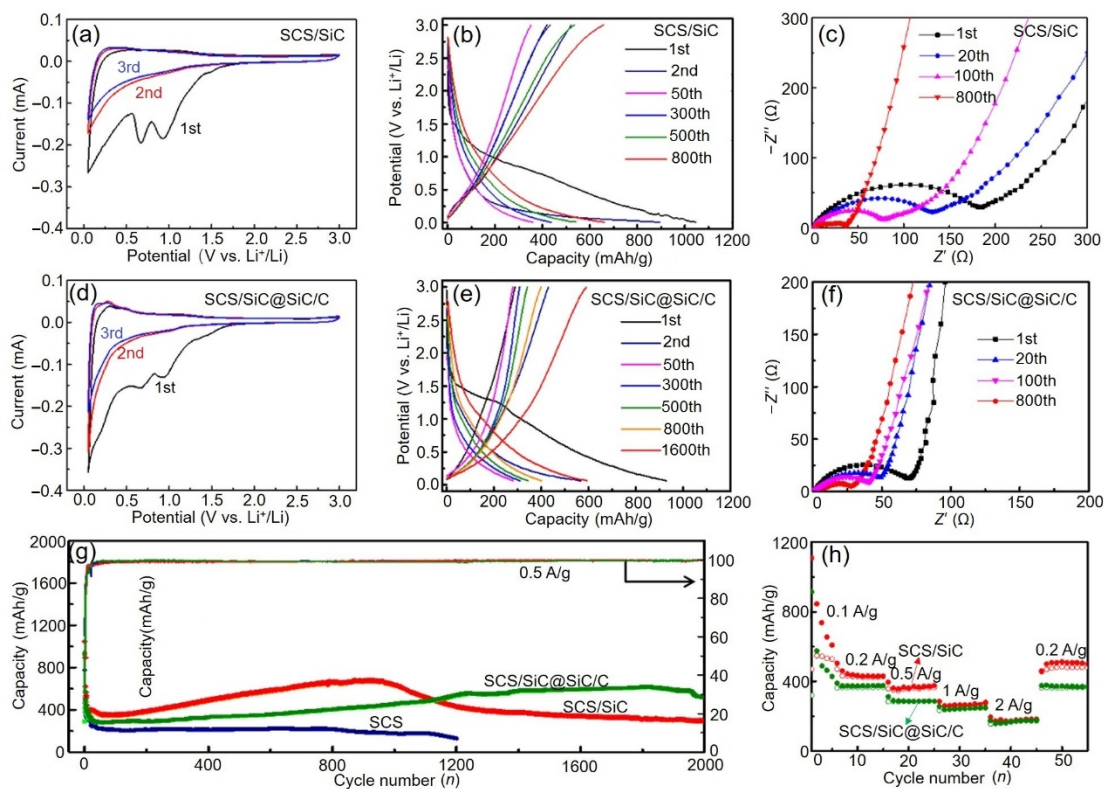

## Graphical Abstract

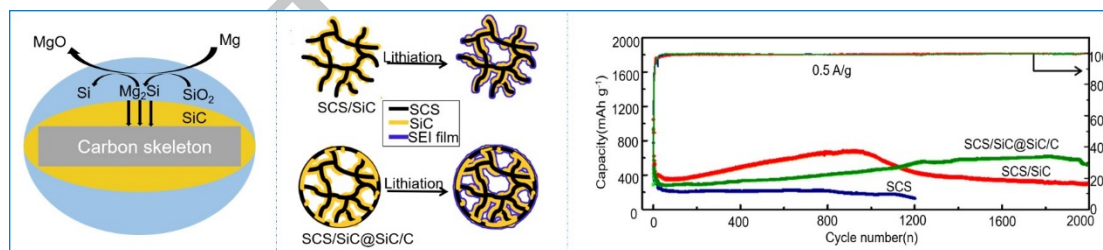

A new hollow nanostructure of sea-sponge-C/SiC@SiC/C has been successfully fabricated by the sea-sponge-C/SiC nanospheres are coated with SiC/C shells through an in situ reduction process, and show an excellent and stable  $\text{Li}^+$  storage capability.

**Title:**

## Hollow nanostructure of sea-sponge-C/SiC@SiC/C for stable Li<sup>+</sup>-storage capability

### Keywords:

SiC, Lithium ion batteries, Cycling stability, Sea-sponge-C/SiC@SiC/C

### Authors:

Weina Li,<sup>†,a</sup> Jiaqi Li,<sup>†,a</sup> Jiahao Wen,<sup>b</sup> Ming Wen,<sup>\*,a</sup> Shipai Chen,<sup>a</sup> Qingsheng Wu,<sup>a</sup>

Yongqing Fu<sup>c</sup>

ACCEPTED MANUSCRIPT